


DRILL HOLE MH 02-38 ASSAY LISTING


| INTERVAL (m) | | | ASSAY DATA (g/t) | |
|--------------|-------|--------|-------------------------|-------------------------|
| FROM | TO | LENGTH | EASTERN ANALYTICAL LTD. | CHM ITEC - BONDAR CLEGG |
| 74.38 | 75.38 | 1.00 | 0.422 | |
| 75.38 | 76.38 | 1.00 | 0.063 | |
| 76.38 | 77.16 | 0.78 | 0.580 | |
| 77.16 | 77.66 | 0.50 | 0.120 | |
| 77.66 | 78.42 | 0.76 | 8.202 | 8.240 |
| 78.42 | 79.72 | 1.30 | 0.191 | |
| 79.72 | 80.47 | 0.75 | 0.417 | |
| 80.47 | 81.22 | 0.75 | 0.207 | |
| 81.22 | 82.22 | 1.00 | 0.005 | |
| 82.22 | 83.22 | 1.00 | 0.005 | |
| 83.22 | 83.82 | 0.60 | 0.207 | |
| 83.82 | 84.12 | 0.30 | 1.374 | |
| 84.12 | 84.81 | 0.69 | 0.457 | 0.407 |
| 84.81 | 85.50 | 0.69 | 0.680 | 0.619 |
| 85.50 | 86.20 | 0.70 | 1.380 | 1.498 |
| 86.20 | 86.90 | 0.70 | 7.125 | 6.474 |
| 86.90 | 87.08 | 0.18 | 1154.348 | 1322.923 |
| 87.08 | 87.63 | 0.55 | 12.803 | 11.138 |
| 87.63 | 88.22 | 0.59 | 10.774 | 9.212 |
| 88.22 | 89.22 | 1.00 | 0.080 | |
| 89.22 | 90.22 | 1.00 | 0.434 | |
| 90.22 | 91.22 | 1.00 | 0.067 | |

Note: Analyses at Eastern Analytical Ltd. were done by metallics screen assay, whereby the total sample was pulverized so that all of the coarse gold could be captured and factored into the analysis, to minimize the "nugget effect" usually associated with mineralization containing free gold. The assay value listed above is thereby a weighted average of the assays of both coarse and fine fractions of the sample. Since all of the coarse fraction of the sample was used by Eastern Analytical Ltd., the check assaying at Chm itec-Bondar Clegg was done only on the fine fraction (-150 mesh) of the samples. The assay value of the fine fraction from Chm itec was combined with the assay value of the coarse fraction from Eastern Analytical to produce a weighted average which is listed above.

01-34 ○ Intersection point with drillhole number, and with grade in g/t gold over true thickness (red-significant gold values, pink-low grade gold values). Values in brackets are higher grade intervals within the mineralized zone.

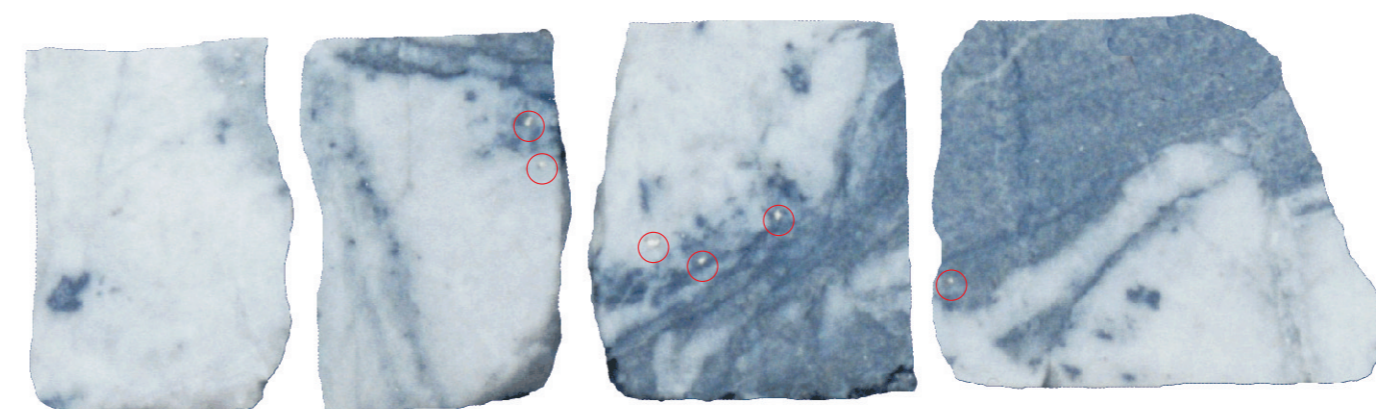

Sample MH.02-38 of high grade vein from the Moosehead Property that assayed 1154g/t. Visible gold (circled) can be observed on the cut surface.

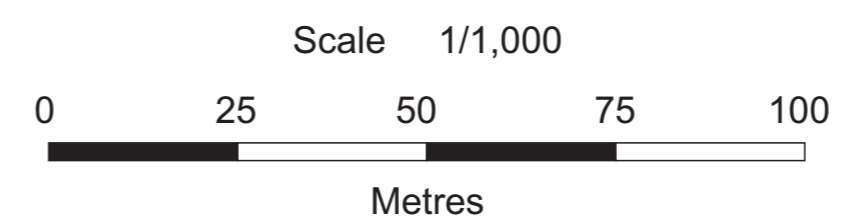

| | | |
|--|---------------------------------------|------------|
| ALTIUS RESOURCES INC. | | License(s) |
| SUDBURY CONTACT MINES | | 8413M |
| MOOSEHEAD PROPERTY | | |
| Composite Longitudinal Section on the North Pond Fault (looking Gridwest) | | |
| Figure No: 1 | Drawn By: D. Barbour | |
| Program: Summer 2002 | Revised By: D. Barbour | |
| NTS: 02E03 & 02D14 | Date Revised: 09-Sept-02 | |
| Scale: 1/1,000 | Filename: North Pond Longitudinal.cdr | |